

Volume 1, Issue 2

Research Article

Date of Submission: 15 Aug, 2025

Date of Acceptance: 05 Sep, 2025

Date of Publication: 25 Sep, 2025

Selective Replenishment of Lithium from Scrap LiFePO₄ Batteries by Using Oxalic Acid

Abhilash Mishra^{1,2*} and Rina Sahu¹

¹National Institute of Technology, Jamshedpur, Jharkhand, India

²ReCy Energy Pvt. Ltd., Pune, Maharashtra, India

*Corresponding Author: Abhilash Mishra, National Institute of Technology, Jamshedpur, Jharkhand, India.

Citation: Mishra, A., Sahu, R. (2025). Selective Replenishment of Lithium from Scrap Lifepo₄ Batteries by Using Oxalic Acid. *Int J Evol Sus Renew Energy Sol*, 1(2), 01-05.

Abstract

The growing demand for EVs has led to an increased need for LFP battery recycling technique. This study introduces an innovative oxalic acid-hydrogen peroxide system for selective leaching of lithium from scrap batteries. By optimizing factors like acid concentration, H₂O₂ volume, pulp density, reaction time, and temperature, a remarkable 99.4% lithium leaching efficiency is achieved with minimal impurity. The optimal conditions for include 10% (w/v) oxalic acid, 5% (v/v) H₂O₂, 100 g/L pulp density, at speed of 300 rpm, and 60°C temperature for 4 hours. Advanced characterization techniques such as XRD and SEM confirm the purity and morphology of the recovered material. This pioneering approach enables closed-loop recycling of LFP batteries, supporting a circular economy, environmental friendly and reducing waste management challenges, ultimately having significant implications for the electric vehicle industries.

Keywords : Black Mass, Hydrometallurgy, LFP battery, Selective Leaching, Oxalic Acid

Introduction

The widespread adoption of lithium iron phosphate (LFP) batteries in EVs is due to their notable characteristics, including cost-effectiveness, high power output, and extended lifespan [1]. The growing demand for LFP batteries has led to a significant increase in their production, with the global market valued at \$17.54 billion in 2023 and projected to reach \$48.95 billion by 2031 [2]. The extensive use of LFP batteries poses substantial economic and environmental concerns and resource conservation. The disposal of scrap LFP batteries can lead to environmental degradation, contaminating groundwater and soil [3]. To mitigate these impacts, recycling has emerged as a vital strategy, enabling the recovery of valuable metals and reducing the economic and environmental costs associated with primary resource extraction. Recovery process includes mechanical processing to recover the black mass. Then black mass is undergone for leaching using various methods, like pyrometallurgy, hydrometallurgy, and bio-hydrometallurgy [4]. Hydrometallurgy is notable for its advantages, including high metal recovery rates, reduced energy consumption, and lower emissions. In hydrometallurgy, strong inorganic acids like HCl, HNO₃, and H₂SO₄ have been used to extract metals from spent LFP batteries [5]. However, the adverse environmental impacts of conventional acid-based extraction methods have sparked interest in organic acids as a viable alternative. Organic acids like oxalic acid, tartaric acid, ascorbic acid, citric acid, and malic acid offer a more environmentally friendly solution [6]. In this research, a novel approach using an oxalic acid-hydrogen peroxide system has been developed to selectively leach lithium metals. This technique provides an efficient, selective, and eco-friendly solution for recovering valuable metals, characterized by cost-effectiveness and operational simplicity. By developing pioneering recycling technologies and refining existing methodologies, the industry can ensure sustainability and reduce waste management challenges.

Materials & Methodology

Materials and Reagents

The study utilized 100 kg of spent prismatic-type LFP batteries provided by Altigreen Pune, India. Commercial-grade oxalic acid (C₂H₂O₄•H₂O₂) and hydrogen peroxide (H₂O₂) were used for leaching studies. Ultrapure de-ionized water was used for sample preparation, dilution and washing.

Disassembling and Pre-processing of LFP Battery

Spent LFP batteries were safely discharged in a 15% sodium chloride (NaCl) solution to prevent potential hazards [7]. Mechanical dismantling was employed to break down the batteries into constituent parts (figure 1). The black mass recovered from the electrode materials by thermal treatment and a hot water rinse to remove impurities.

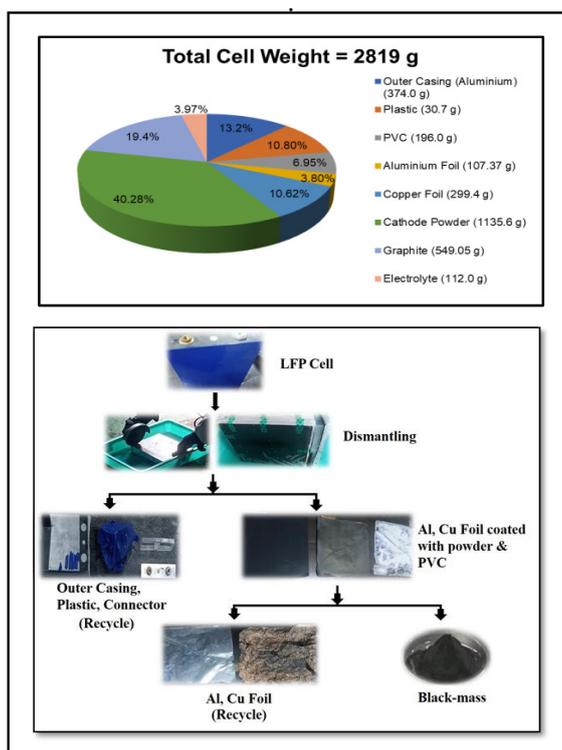


Figure 1: Composition & Disassembling of LFP Batteries

Leaching of Black Mass Powder

Oxalic acid was chosen for leaching due to its environmentally friendly profile and targeted extraction capabilities. A measured amount of black mass was introduced into a solution of oxalic acid, water, and hydrogen peroxide, maintaining a consistent temperature. The resulting suspension was filtered using Whatman No. 42 filter paper, and the retained residue was washed with de-ionized water and then dried in an oven at 130°C for 24 hours.

The efficiency of metal leaching was determined using the following formula (1):

$$\% \text{ Leaching efficiency} = \frac{C_E * V}{C_o * m} * 100 \quad (1)$$

In the formula, C_E denotes metal concentration in the leachate solution (g/L), V represents the total volume of the leachate (L), C_o signifies initial metal content in the black mass (weight %), and m corresponds to the mass of black mass subjected to leaching (g). The leachate solutions were analyzed using ICP-OES and AAS, while the residues were characterized through comprehensive chemical analysis, SEM and XRD techniques. To ensure accuracy, all experiments were performed in replicate, and the average results were utilized to determine the final metal recovery percentages.

Result and Discussion

Characterization of Black Mass Powder

The black mass powder underwent characterization to determine its elemental composition and structural properties. ICP-OES (Thermo Scientific iCAP 7600 pair instrument) and AAS (Shimadzu AA-7000F spectroscopy) analysis revealed significant amounts of lithium (3.13%), iron (13.7%), phosphorus (7.3%), copper (0.17%), and aluminum (0.23%). XRD analysis identified distinct phases, including lithium iron phosphate (LiFePO_4) and iron phosphate (FePO_4) (figure 2). Scanning electron microscopy showed particles with irregular shapes and sizes, indicating a heterogeneous distribution (figure 2). These findings highlight the complex composition and morphology of the material before leaching. The results demonstrate the material's intricate nature, comprising various elements and phases, which is crucial for optimizing leaching processes and further analysis.

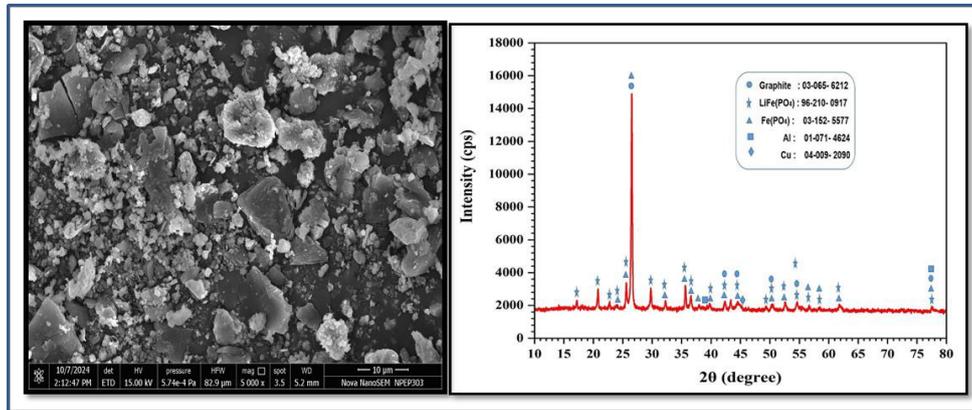


Figure 2: SEM & XRD of Spent LFP Black Mass Powder

Effect of Different Leaching Parameters

The environmentally friendly and cost-effective properties of oxalic acid made it an ideal choice for selective leaching of lithium. A parametric study was conducted to optimize lithium extraction from scrap LFP black mass, examining the effects of oxalic acid concentration, H₂O₂, pulp density, reaction time, and temperature.

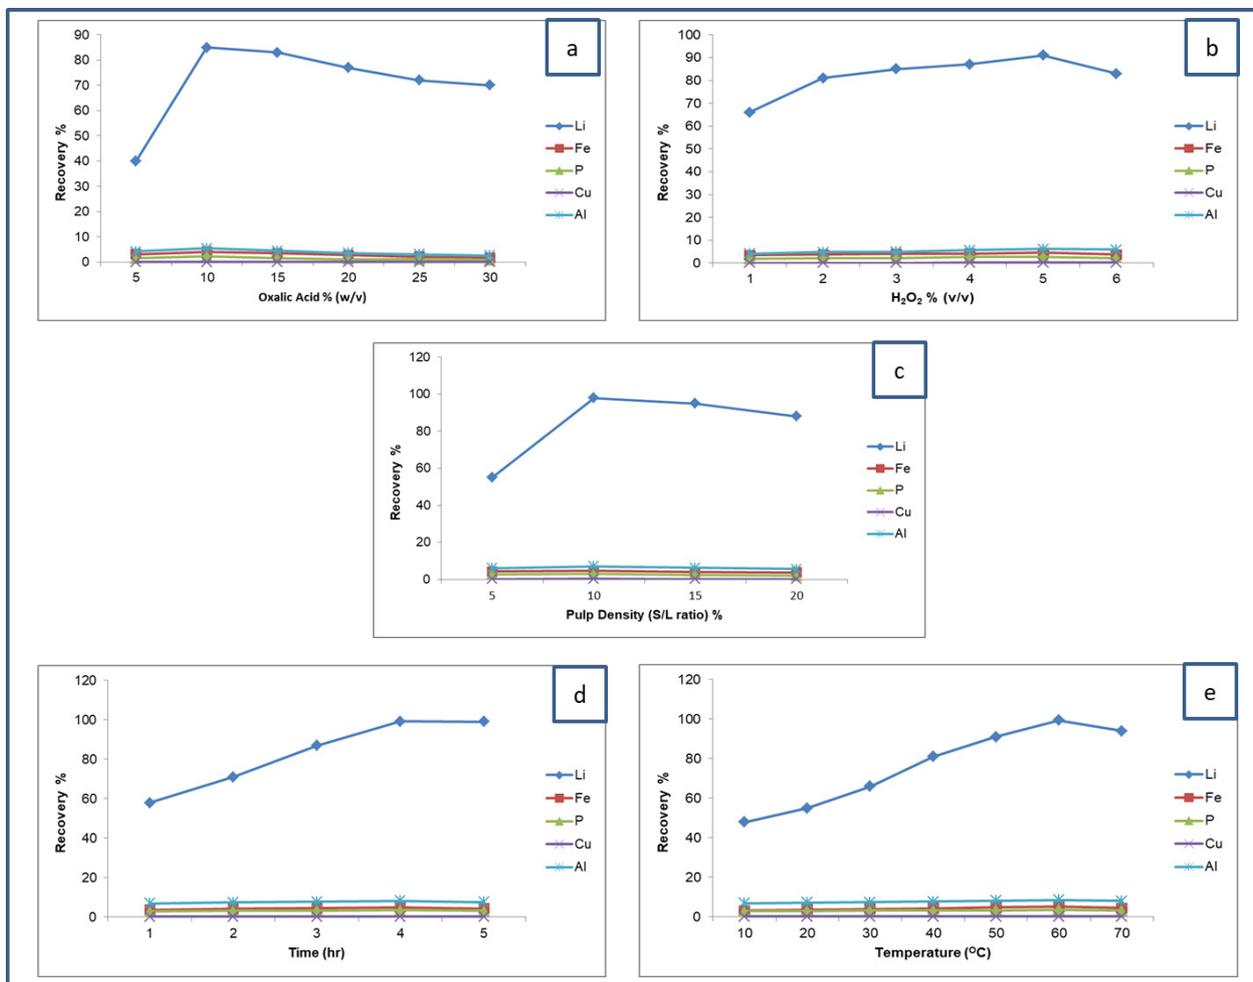


Figure 3: Influence of Oxalic Acid Concentrations(a), H₂O₂ Volume(b), Pulp Density(c), Reaction Time(d) and Temperature(e) on Leaching Efficiency

Effect of Oxalic Acid Concentration

The influence of oxalic acid concentration on the leaching efficiencies of various metals was investigated. From Figure 3(a), it is evident that increasing the oxalic acid concentration from 5% to 10% (w/v) improved leaching efficiencies of lithium (from 80% to 95%), iron (from 2.5% to 4.2%), copper (from 0.05% to 0.15%), aluminium (from 4% to 6%), and phosphorus (from 1.5% to 2.5%). The optimal concentration of 10% (w/v) oxalic acid is likely due to the sufficient availability of protons and acid radicals necessary for metal leaching. Further increases beyond 15-30% (w/v) resulted in marginal improvements, possibly due to increased ionic strength hindering further leaching [8].

Effect of H2O2

This section includes the effect of H₂O₂ on leaching efficiency, as shown in Figure 3(b), increasing H₂O₂ concentrations significantly improved leaching efficiencies. The optimal concentration of 5% (v/v) H₂O₂ is likely due to the effective breakdown of organic materials, conversion of Fe²⁺ to Fe³⁺, and disruption of mineral structures, enhancing metal recovery. Beyond 5% (v/v), excessive oxidation may lead to the formation of insoluble compounds, reducing metal recovery [6].

Effect of Pulp Density (S/L Ratio)

The levels of oxalic acid in solutions tend to be greater when pulp density is lower. As evident from Figure 3(c), a pulp density of 10% emerged as the optimal level, likely due to the optimal balance between oxalic acid availability and metal ion concentration. Higher pulp densities may result in decreased leaching efficiencies due to increased pH and reduced metal solubility [9].

Effect of Reaction Time

The effect of reaction time on the leaching efficiencies of various metals was investigated. As shown in Figure 3(d), longer reaction times significantly boosted leaching efficiency, with 4 hours being the optimal duration. This is likely due to the sufficient time allowed for reactants to diffuse into the black mass and products to emerge from the solid matrix [10].

Effect of Temperature

The impact of temperature on the leaching depicted in Figure 3(e), the study revealed that 60°C is the optimal temperature, likely due to the enhanced molecular energy and diffusion rates promoting metal recovery. Temperatures above 60°C may lead to decreased efficiency due to reductant instability and accelerated H₂O₂ decomposition [7]. The optimal conditions for maximizing leaching efficiency were determined to be 10% (w/v) oxalic acid, 5% (v/v) H₂O₂, 10% pulp density, 4 hours reaction time, and 60°C temperature.

Characterization of Residue After Leaching

After leaching, the slurry was filtered, and the residue was rinsed and dried. Analysis showed the leach liquor was rich in lithium, while the residue mainly consisted of iron (13.02%) and phosphate (7.03%). SEM analysis revealed significant morphological transformations, with particles forming aggregates with prismatic structures (figure 4). XRD analysis (figure 4) identified phases of FePO₄ and FeC₂O₄•2H₂O, indicating significant dissolution of LiFePO₄. This analysis shows the leaching process effectively separated lithium from the black mass powder, resulting in a residue with distinct compositional characteristics. The residue's primary constituents were FePO₄ and FeC₂O₄•2H₂O.

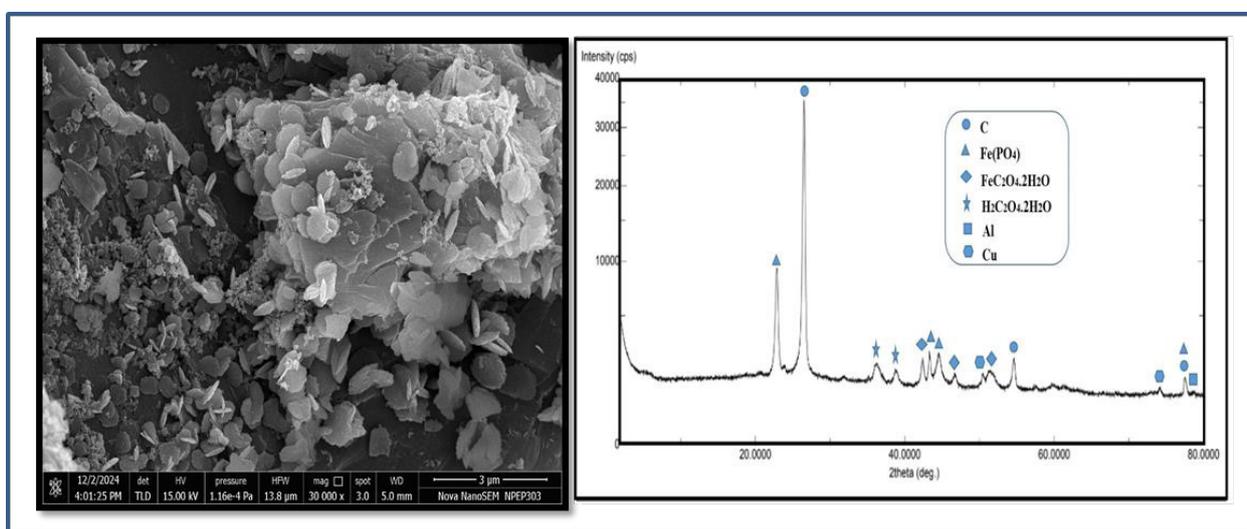


Figure 4: SEM & XRD of Black Mass Powder After Leaching

Conclusion

This study presents a pioneering eco-friendly approach to extract lithium from spent lithium-iron phosphate (LiFePO₄) batteries. Optimal leaching conditions were established, including 10% (w/v) oxalic acid combined with 5% (v/v) H₂O₂, a pulp density of 100 g/L, at speed of 300 rpm, and temperature of 60°C for 4 hours. Under these conditions, the oxalic acid-hydrogen peroxide leaching system achieved a remarkable lithium leaching efficiency of 99.4%, with minimal co-leaching of other metals. The leaching residues primarily consisted of FeC₂O₄•2H₂O, a valuable precursor for LiFePO₄ synthesis. Characterization results using ICP-OES and XRD confirmed the high purity and morphology of the recovered lithium. ICP-OES analysis detected the presence of various elements in the black mass, while XRD analysis revealed the composition of the leaching residues. This process promotes a circular economy, reduces environmental impacts, and supports sustainable energy storage, alleviating waste management challenges and paving way for eco-friendly future.

References

1. Li, P., Liu, Q., Møller, M., Wang, D., Jensen, L.R., Xia, X., 2024. Direct regeneration of spent lithium-ion batteries: A mini-review. *Materials Letters* 357, 135724.
2. Lu, Y., & Zhu, T. (2024) Status and Prospects of Lithium Iron Phosphate Manufacturing in the Lithium Battery Industry. *MRS Communications*, 14, 888-899.
3. Alipanah, M., Saha, A. K., Vahidi, E., Jin, H., & Tenório, J. A. S. (2021). Value recovery from spent lithium-ion batteries: A review on technologies, environmental impacts, economics, and supply chain. *Clean Technologies and Recycling*, 1(2), 152-184.
4. Mrozik, W., Rajaeifar, M. A., Heidrich, O., & Christensen, P. (2021). Environmental impacts, pollution sources and pathways of spent lithium-ion batteries. *Energy Environ. Sci*, 14, 6099-6121.
5. Yadav, P., Jie, C. J., Tan, S., & Srinivasan, M. (2020). Recycling of cathode from spent lithium iron phosphate batteries. *Journal of Hazardous Materials*, 399, 123068.
6. Mahandra, H., & Ghahreman, A. (2021). A sustainable process for selective recovery of lithium as lithium phosphate from spent LiFePO₄ batteries. *Resources, Conservation and Recycling*, 175, 105883.
7. Mishra, A., & Sahu, R. (2025). Cutting-Edge Recycling Solution at Pilot-Scale for End-of-Life LiFePO₄ Batteries and Recovery of Graphite Using Centrifuge Filtration. *Particuology*, 99, 11-22.
8. Li, L., Lu, J., Zhai, L., Zhang, X., Curtiss, L., Jin, Y., ... & Amine, K. (2018). A facile recovery process for cathodes from spent lithium iron phosphate batteries by using oxalic acid. *CSEE Journal of Power and Energy Systems*, 4(2), 219-225.
9. Zheng, R., Zhao, L., Wang, W., Liu, Y., Ma, Q., Mu, D., Li, R., Dai, C., (2016). Optimized Li and Fe recovery from spent lithium-ion batteries via a solution-precipitation method. *RSC Adv.* 6(49), 43613-43625
10. Luo, Z., Shu, J., Chen, M., Wang, R., Zeng, X., Yang, Y., Wang, R., Chen, S., Liu, R., Liu, Z., Su, Z., Yu, K., Deng, Y., et al., (2021). Enhanced leaching of manganese from low-grade pyrolusite using ball milling and electric field. *Ecotoxicol. Environ. Saf.* 211, 111893.